

Change of Antiferromagnetic Structure near a Quantum Critical Point in $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$

M. Yokoyama,¹ N. Oyama,¹ H. Amitsuka,² S. Oinuma,²
I. Kawasaki,² K. Tenya,³ M. Matsuura,⁴ K. Hirota,^{4,5} and T.J. Sato⁴

¹*Faculty of Science, Ibaraki University, Mito 310-8512, Japan*

²*Graduate School of Science, Hokkaido University, Sapporo 060-0810, Japan*

³*Faculty of Education, Shinshu University, Nagano 380-8544, Japan*

⁴*Neutron Science Laboratory, Institute for Solid State Physics,
The University of Tokyo, Tokai 319-1106, Japan*

⁵*Graduate School of Science, Osaka University, Toyonaka 560-0043, Japan*

(Dated: May 14, 2008)

The elastic neutron scattering experiments were carried out on the solid solutions $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$ to clarify the nature of the antiferromagnetic (AF) state in the vicinity of the quantum critical point (QCP): $x_c \sim 0.8$. The incommensurate AF order with the wave vector of $q_h = (1/2, 1/2, \sim 0.3)$ observed in pure CeRhIn_5 is weakly suppressed upon doping with Co, and a commensurate $q_c = (1/2, 1/2, 1/2)$ and an incommensurate $q_1 = (1/2, 1/2, \sim 0.42)$ AF structures evolve at intermediate Co concentrations. These AF orders are enhanced at $x = 0.7$, and furthermore the q_h AF order vanishes. These results suggest that the AF correlations with the q_c and q_1 modulations are significantly enhanced in the intermediate x range, and may be connected with the evolution of the superconductivity observed above $x \sim 0.3$.

PACS numbers: 71.27.+a, 74.70.Tx, 75.25.+z,

I. INTRODUCTION

The interplay between magnetism and superconductivity (SC) in the vicinity of a quantum critical point (QCP) is one of the most intriguing subjects in the heavy-fermion systems. The QCP is characterized by the phase transition at zero temperature, which is generated by suppressing a magnetically ordered state via changing pressure, magnetic field and chemical composition. The SC often emerges near the QCP, and it is therefore believed that the magnetic fluctuation enhanced near the QCP plays a crucial role in the formation of the Cooper pairs. The recently discovered heavy-fermion compounds CeMIn_5 ($M = \text{Rh}$ and Co ; HoCoGa_5 -type tetragonal structure) provide a unique opportunity to investigate this subject. CeCoIn_5 is an unconventional superconductor characterized by an anomalously large specific-heat jump ($\Delta C/\gamma T_c = 4.3$) at transition temperature $T_c = 2.3$ K.¹ A strong Pauli-limiting effect gives rise to a first-order transition at SC critical field H_{c2} below 0.7 K.^{2,3} In addition, above H_{c2} the non-Fermi-liquid behavior is observed in the temperature variations of the specific heat and the resistivity, which is considered to be due to the effect of quantum-critical fluctuation induced in the proximity of antiferromagnetism.⁴ On the other hand, CeRhIn_5 shows an incommensurate (IC) antiferromagnetic (AF) order below $T_N = 3.8$ K at ambient pressure, whose structure has been proposed to be a helical (spiral) with a propagation vector of $q_h = (1/2, 1/2, 0.297)$.^{5,6} As pressure P is applied, T_N initially increases to 4 K ($P = 0.8$ GPa), and then rapidly decreases with further increasing P . At the same time, the SC develops above 1 – 1.5 GPa. T_c increases with increasing P and merges with T_N at the critical pressure

$P_c = 1.9$ GPa.^{7,8,9,10}

It is interesting to investigate the relationship between the IC-AF and SC phases for CeRhIn_5 and CeCoIn_5 . The specific-heat, magnetization, and resistivity measurements^{11,12} for mixed compounds $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$ revealed that the IC-AF phase for pure CeRhIn_5 is weakly suppressed upon doping with Co, and then vanishes at the QCP: $x_c \sim 0.8$. The SC phase appears above $x = 0.4$, suggesting the coexistence of both phases for intermediate Co concentrations. The obtained $x - T$ phase diagram is quite similar to the $P - T$ phase diagram for pure CeRhIn_5 . Recently, we found from the neutron scattering experiments that a commensurate (C) AF order with a modulation of $q_c = (1/2, 1/2, 1/2)$ evolves in the IC-AF phase at $x \sim 0.4$.^{13,14} This suggests that the C-AF correlation is tightly coupled with the SC. We expect that further insight on the role of the C- and IC-AF correlations to the SC is obtainable from both the bulk and microscopic investigations on a wide x range. In addition, it is remarkable that the recently proposed $x - T$ phase diagram¹⁵ differs from previous one,¹¹ while it involves the C-AF phase in intermediate x range. We have thus performed the specific heat and neutron scattering experiments on $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$ with entire x range to clarify the characteristics of AF states near the QCP and find similarity or difference between them and the previously reported ones.

II. EXPERIMENTAL DETAILS

Single crystals of $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$ were grown from an In flux with appropriate amounts of Ce, Rh and Co as starting materials. We prepared rod-type sam-

ples along the tetragonal $[1\bar{1}0]$ direction (typical size of $\sim 1.6 \times 1.6 \times 15 \text{ mm}^3$) for neutron scattering measurements by cutting out from the large ingots of the single crystal, and small pieces of single crystal for specific heat measurements. The electron probe microanalysis (EPMA) measurements for the sample used in the specific heat and neutron scattering experiments indicate that the estimated Rh/Co concentrations x significantly deviate from the nominal (starting) values, which occurs frequently in the sample grown by the flux technique. Similar deviation of x is also observed in the samples investigated previously:¹³ x for the samples used in bulk and neutron scattering measurements were estimated to be 0.45 and 0.53, respectively, while the nominal x was 0.4. In fact, a crucial problem on the reproducibility caused by the large distribution of x was found in several samples. We will thus use the samples with homogeneous distribution of x being achieved within a few percent error, and adopt the x value estimated from the EPMA measurements for each sample throughout this article.

Specific heat C_P was measured using a thermal relaxation method in a commercial ^3He refrigerator (Oxford Instruments) from 0.5 K to 100 K. Elastic neutron scattering experiments for $x = 0.05(1), 0.23(2), 0.43(2), 0.53(2)$ and $0.70(3)$ were performed on the triple-axis spectrometers GPTAS (4G) and PONTA (5G) located at the JRR-3M research reactor of the JAEA, Tokai. The neutron momentum $k = 3.83 \text{ \AA}^{-1}$ was chosen with the (002) reflection of the pyrolytic graphite (PG) for both monochromator and analyzer, and a set of $40^\circ\text{-}40^\circ\text{-}40^\circ\text{-}80^\circ$ collimators together with two PG filters was used. The samples were mounted in standard Al capsules filled with ^4He gas so that the scattering plane becomes (hhl) , and cooled down to 1.5 K in a pumped ^4He cryostat. In this geometry the sample rod is perpendicular to the scattering plane, enabling to minimize an effect of high neutron absorption by Rh and In. The neutron penetration length in the samples for the present k value was calculated to be $\sim 1.8 \text{ mm}$.

III. RESULTS AND DISCUSSION

Figure 1 shows temperature variations of the specific heat divided by temperature C_P/T . A jump associated with the IC-AF order is clearly seen at $T_{Nh} = 3.8 \text{ K}$ for $x = 0.05$. The magnitude of the jump is reduced with increasing x , and then the jump becomes obscure around $\sim 2.8 \text{ K}$ at $x = 0.7$. A kink anomaly appears at $T_{Nc} \sim 2.8 \text{ K}$ in C_P for $0.22 \leq x \leq 0.45$ (see the inset of Fig. 1), which originates from the C-AF order.¹³ The evolution of the SC yields another jump in C_P/T at $T_c = 1.4 - 2 \text{ K}$ for $x \geq 0.29$, whose magnitude increases with increasing x . It seems that the entropy release estimated from C_P/T below T_c is not simply balanced. This indicates the existence of large residual entropy below T_c , which is actually evidenced in pure CeCoIn_5 from the C_P/T data taken under strong magnetic fields.¹ This

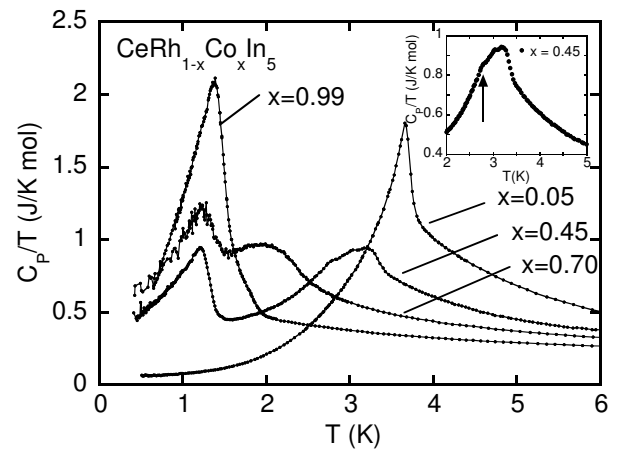


FIG. 1: Temperature variations of the specific heat divided by temperature C_P/T for $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$. The enlargement around 3 K for $x = 0.45$ is shown in the inset.

feature may be linked with the increase in C_P/T above T_{Nh} for the lower Co concentrations, suggesting that the magnetic critical fluctuation develops around x_c as a consequence of the suppression of the AF order. These results on C_P are basically consistent with the previous reports.^{11,12,15}

In Fig. 2, we plot the $x - T$ phase diagram estimated from our C_P/T data. Here we define T_{Nh} and T_c as the onset of the jump in C_P/T , and T_{Nc} as the position of the kink anomaly. The T_{Nh} and T_c values as well as the shape of the $x - T$ phase diagram of ours are reasonably comparable to those in the first report.¹¹ On the other hand, although an ambiguity on the determination of the transition temperatures still remains, there is a qualitative difference between our $x - T$ phase diagram and recently proposed one:¹⁵ former involves both the IC- and C-AF phases in the intermediate x range while latter does only the C-AF phase. The strong sample quality dependence may be responsible for such differences. Nevertheless, it is interesting that our $x - T$ phase diagram for $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$, including the existence of the C-AF order and the SC, is quite similar to that for the isostructural Ir-doped system $\text{CeRh}_{1-x}\text{Ir}_x\text{In}_5$.¹⁶

Displayed in Fig. 3 are neutron scattering patterns for the momentum transfers $Q = (1/2, 1/2, 1+\zeta)$ ($0 \leq \zeta \leq 1$) obtained at 1.5 K, where the instrumental backgrounds were carefully subtracted using data at 5 K. A set of satellite Bragg peaks characterized by a single wave vector $q_h = (1/2, 1/2, 0.295(3))$ was observed for $x = 0.05$. Similar peaks also appear at $x = 0.23$, whose modulation corresponds to that for $x = 0.05$ within the experimental accuracy. These peaks can be attributed to the occurrence of the IC-AF order, the same as that found in pure CeRhIn_5 .⁶ We cannot find any peak due to the other AF order at $x = 0.23$, while C_P at $x = 0.22$ shows the kink at T_{Nc} as well as the jump at T_{Nh} . These Co concentrations are the boundary on the oc-

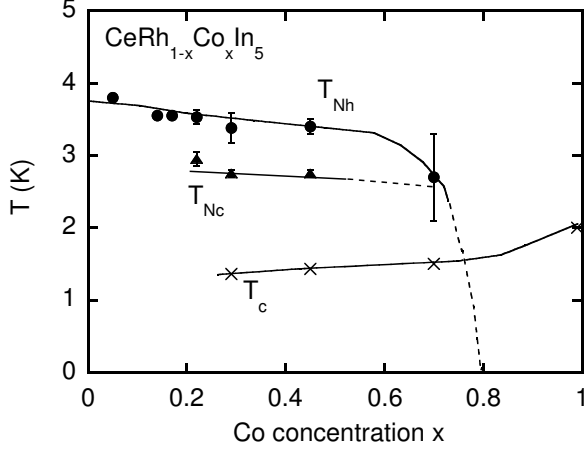


FIG. 2: The $x-T$ phase diagram estimated from the C_P/T data for $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$. T_{Nh} and T_c are determined by the onset of the jump in C_P/T , while T_{Nc} by the kink anomaly. The lines are guides to the eye.

currence of the kink in C_P . We thus consider this inconsistency coming from a few percent error of x in these samples. At $x = 0.43$, we observed the evolution of new AF Bragg peaks ascribed to the AF order with the C $q_c = (1/2, 1/2, 1/2)$ structure together with the IC-AF Bragg peaks. The modulation of the IC-AF order slightly changes to $q_h = (1/2, 1/2, 0.303(4))$. In addition, weak peaks are detected at $Q = (1/2, 1/2, 0.40(1))$ ($\equiv q_1$) and its corresponding positions. However this order is considered to occur in a shorter range along the c axis because the widths of these Bragg peaks are very large. These results for $x = 0.43$ reproduce fairly well our previous report.¹³ We confirmed using polarized neutron scattering technique that all of these peaks originate from the alignments of the magnetic moments.¹⁴ At $x = 0.7$, on the other hand, the AF orders with q_c and $q_1 = (1/2, 1/2, 0.416(5))$ modulations are enhanced, and simultaneously the q_h -AF order vanishes. The widths of these Bragg peaks seem to approach the resolution limit (about a few hundred Å in the length). We also checked a possibility of the other AF state appearing by the scan at $Q = (0, 0, 1 + \zeta)$ ($0 \leq \zeta \leq 1$) for $x = 0.43$ and 0.7 , but no additional Bragg peak is detected.

The magnitudes of the volume-averaged AF moments μ_h , μ_1 and μ_c for the q_h , q_1 and q_c structures, respectively, were estimated from the integrated intensities of the magnetic Bragg peaks obtained by the longitudinal and transverse scans, where the intensities of the weak nuclear (110) Bragg peak were used as a reference. In accordance with the previous reports,^{6,13,17} we assume that both the IC-AF orders have the helical structures, and the ordered moments in all the AF states lie in the tetragonal basal plane [Fig. 4(a)]. For all the AF states, the AF Bragg-peak intensities divided by the polarization factor calculated on the basis of above assumptions roughly follow the $|Q|$ dependence of the Ce^{3+} magnetic

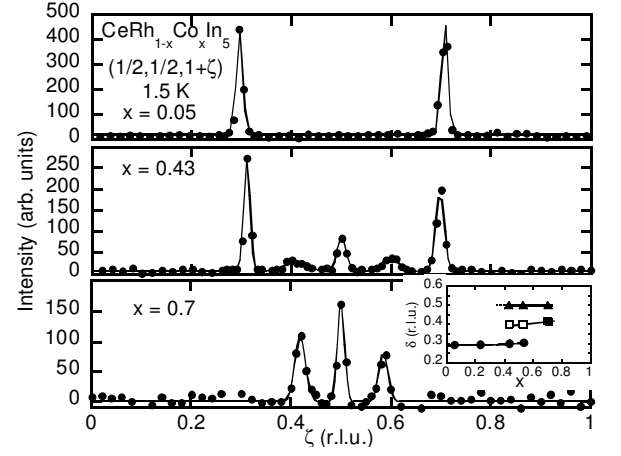


FIG. 3: Neutron scattering pattern at 1.5 K for $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$ with $x = 0.05$, 0.43 and 0.7 , obtained by scans at $Q = (1/2, 1/2, 1 + \zeta)$ ($0 \leq \zeta \leq 1$). The inset shows x variations of the AF modulation $q = (1/2, 1/2, \delta)$.

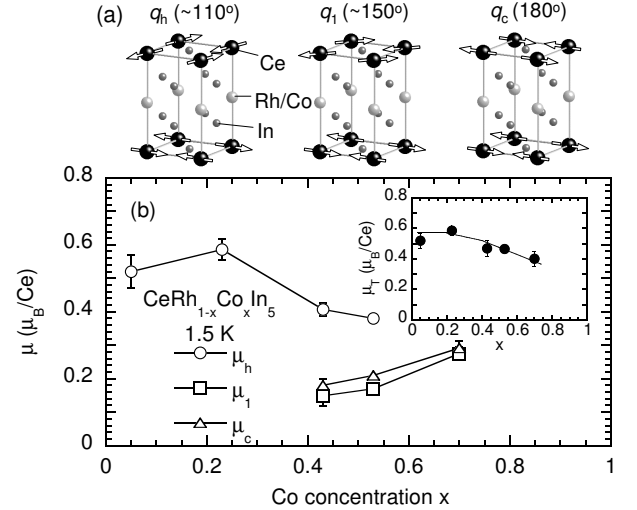


FIG. 4: (a) Arrangements of the magnetic moment on Ce ions for helical (q_h and q_1) and commensurate (q_c) AF structures, and (b) x variations of the AF moments μ_h , μ_1 and μ_c at 1.5 K for $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$. An angle between nearest neighbor moments along the c axis for each structure is also shown in (a). The inset in (b) indicates x variations of the total AF moment at 1.5 K, defined by $\mu_T = (\mu_h^2 + \mu_1^2 + \mu_c^2)^{1/2}$.

form factor.¹⁸ The x variations of μ_h , μ_1 and μ_c at 1.5 K are shown in Fig. 4(b). The μ_h values at $x = 0.05$ and 0.23 are estimated to be $0.51(5) \mu_B/\text{Ce}$ and $0.59(2) \mu_B/\text{Ce}$, which are close to the values $(0.59 - 0.75 \mu_B/\text{Ce})$ at $x = 0$.^{6,19} For $x \geq 0.43$, μ_1 and μ_c increase in connection with a reduction of μ_h , and reach $0.27(2) \mu_B/\text{Ce}$ and $0.29(2) \mu_B/\text{Ce}$ at $x = 0.7$, respectively. The total AF moment $\mu_T \equiv (\mu_h^2 + \mu_1^2 + \mu_c^2)^{1/2}$ shows a weak decrease as x approaches $x_c \sim 0.8$.

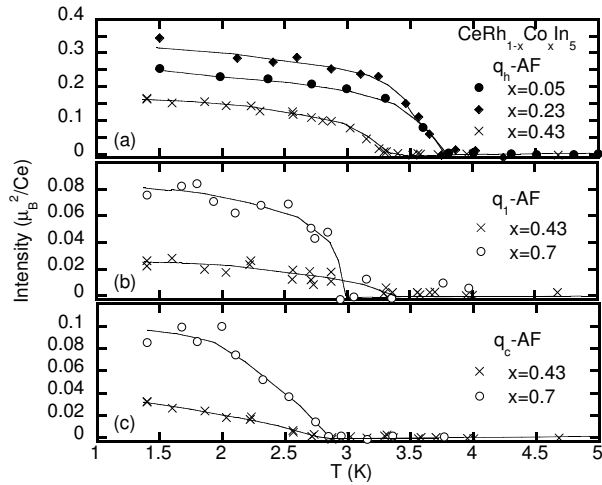


FIG. 5: Temperature variations of the AF Bragg-peak intensities for (a) q_h , (b) q_1 and (c) q_c structures in $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$, which are mainly estimated at the $Q = (1/2, 1/2, \sim 1.3)$, $(1/2, 1/2, \sim 1.41)$, and $(1/2, 1/2, 3/2)$ positions, respectively. The lines are guides to the eye.

Temperature variations of the AF Bragg-peak intensities $I_h(T)$, $I_1(T)$ and $I_c(T)$ for q_h , q_1 and q_c structures are plotted in Fig. 5. We observed that $I_h(T)$ for $x = 0.05$ and 0.23 start increasing at 3.8 K, and then show a tendency to be constant below ~ 3 K. At $x = 0.43$, comparable $I_h(T)$ function is seen, but its onset is reduced to 3.4 K. The Bragg-peak intensity due to the q_1 -AF ordering (but short-ranged) coincidentally develops at almost the same temperature. The onsets of $I_h(T)$ agree with T_{Nh} defined by the jump anomalies in C_P . $I_c(T)$ for $x = 0.43$ starts increasing at 2.7 K, where we observed the kink anomaly in C_P . $I_c(T)$ follows a T -linear function in the wide temperature range. At $x = 0.7$, on the other hand, the onset of $I_1(T)$ gets close to that of $I_c(T)$ around 2.9 K, where the broadened jump anomaly is observed in C_P . The different types of AF correlations exist with nearly the same energy scale, which may be responsible for such temperature dependence of $I_c(T)$. It should be noted that none of the $I_h(T)$ and $I_1(T)$ curves for all x shows the reduction due to the appearance of the C-AF state. This strongly suggests that the C-AF order does not replace the IC-AF order but coexists with it in the sample, although it is still unclear whether the coexistence occurs in microscopic scale or not.

It is observed that the AF orders with the q_c and q_1 modulations simultaneously develop with increasing x , followed by the suppression of the q_h -AF order. This indicates that the AF correlations with the C modulation q_c and its neighbor q_1 are significantly enhanced as x approaches x_c : the quantum critical behavior is generated by the suppression of the AF order with q_c and q_1 rather than the q_h -AF order, and may be connected with the evolution of the SC. Such a variation of the AF correlation is expected to influence strongly

the low-energy magnetic fluctuations. For CeRhIn_5 , it is pointed out that the AF fluctuation with the q_h modulation develops at temperature much higher than T_{Nh} , and this may yield the increase in C_P/T above T_{Nh} .²⁰ Recent inelastic neutron scattering experiments using a high energy-precision spectrometer revealed that the modulation of the AF fluctuation does not concentrate on q_h , but spreads widely along the $q = (1/2, 1/2, \zeta)$ line in the q -space.²¹ For CeCoIn_5 , on the other hand, recent inelastic neutron scattering experiments revealed the evolution of the magnetic excitation with the C q_c modulation associated with the SC transition,²² which is considered to be the evidence of the coupling between the C q_c -AF correlation and the SC. We suggest from these features on the AF fluctuation that the AF correlations with various propagation vector at around $\sim q_c$ on the $q = (1/2, 1/2, \zeta)$ line cooperatively (or competitively) emerge in the intermediate x range of $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$, leading to the complicated AF orders at $x \sim x_c$. Recent de Haas van Alphen experiments for $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$ revealed a dramatical change in the topology of the Fermi surface at much lower Co concentration than x_c ,²³ which is expected to strongly influence the variations of the AF structure presently observed.

A simple relationship between the AF order and the SC rather than that seen in $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$ is realized in the $\text{CeCo}(\text{In}, \text{Cd})_5$ system.²⁴ Doping Cd into CeCoIn_5 is found to suppress the SC phase, and then generate the AF phase above $\sim 10\%$ Cd concentration. This AF phase involves only the C q_c structure.²⁵ In addition, the AF transition temperature monotonically increases to ~ 5 K with increasing the Cd content up to 30% . These properties of the AF state contrast sharply with those found in $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$, where we observed the AF orders having both C and IC modulations and the AF transition temperature to be kept at ~ 3.8 K as x decreases from x_c . We consider that such differences may be due to the effect of the IC-AF correlations with q_h involved in $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$.

IV. SUMMARY

The present neutron scattering and specific heat measurements for $\text{CeRh}_{1-x}\text{Co}_x\text{In}_5$ confirmed that both the AF and SC appear in a wide x range, which is consistent with the previous reports.^{11,12} The AF order with the q_h structure is suppressed with increasing x , and both the q_c and q_1 structures emerge in the intermediate x range. This suggests that the AF correlations with the C q_c and its neighbor q_1 may be tightly coupled with the evolution of the SC.

Acknowledgments

We thank N. Aso for informative discussions. This work was supported by a Grant-in-Aid for Scientific Re-

-
- ¹ C. Petrovic, P. G. Pagliuso, M. F. Hundley, R. Movshovich, J. L. Sarrao, J. D. Thompson, Z. Fisk and P. Monthoux, *J. Phys.: Condens. Matter* **13**, L337 (2001).
 - ² K. Izawa, H. Yamaguchi, Y. Matsuda, H. Shishido, R. Settai and Y. Onuki, *Phys. Rev. Lett.* **87**, 057002 (2001).
 - ³ T. Tayama, A. Harita, T. Sakakibara, Y. Haga, H. Shishido, R. Settai and Y. Onuki, *Phys. Rev. B* **65**, 180504(R) (2002).
 - ⁴ A. Bianchi, R. Movshovich, I. Vekhter, P. G. Pagliuso and J. L. Sarrao, *Phys. Rev. Lett.* **91**, 257001 (2003).
 - ⁵ H. Hegger, C. Petrovic, E. G. Moshopoulou, M. F. Hundley, J. L. Sarrao, Z. Fisk and J. D. Thompson, *Phys. Rev. Lett.* **84**, 4986 (2000).
 - ⁶ W. Bao, P. G. Pagliuso, J. L. Sarrao, J. D. Thompson, Z. Fisk, J. W. Lynn and R. W. Erwin, *Phys. Rev. B* **62**, R14621 (2000); *Phys. Rev. B* **67**, 099903(E) (2003).
 - ⁷ T. Mito, S. Kawasaki, G.-q. Zheng, Y. Kawasaki, K. Ishida, Y. Kitaoka, D. Aoki, Y. Haga and Y. Onuki, *Phys. Rev. B* **63**, 220507(R) (2001).
 - ⁸ G. Knebel, D. Aoki, D. Braithwaite, B. Salce and J. Flouquet, *Phys. Rev. B* **74**, 020501(R) (2006).
 - ⁹ G. F. Chen, K. Matsubayashi, S. Ban, K. Deguchi and N. K. Sato, *Phys. Rev. Lett.* **97**, 017005 (2006).
 - ¹⁰ M. Yashima, S. Kawasaki, H. Mukuda, Y. Kitaoka, H. Shishido, R. Settai and Y. Onuki, *Phys. Rev. B* **76**, 020509(R) (2007).
 - ¹¹ V. S. Zapf, E. J. Freeman, E. D. Bauer, J. Petricka, C. Sirvent, N. A. Frederick, R. P. Dickey and M. B. Maple, *Phys. Rev. B* **65**, 014506 (2001).
 - ¹² J. R. Jeffries, N. A. Frederick, E. D. Bauer, H. Kimura, V. S. Zapf, K.-D. Hof, T. A. Sayles and M. B. Maple, *Phys. Rev. B* **72**, 024551 (2005).
 - ¹³ M. Yokoyama, H. Amitsuka, K. Matsuda, A. Gawase, N. Oyama, I. Kawasaki, K. Tenya and H. Yoshizawa, *J. Phys. Soc. Jpn.* **75**, 103703 (2006).
 - ¹⁴ M. Yokoyama, N. Oyama, H. Amitsuka, S. Oinuma, I. Kawasaki, K. Tenya, M. Matsuura and K. Hirota, *Physica B* **403**, 812 (2008).
 - ¹⁵ S. Ohira-Kawamura, H. Shishido, A. Yoshida, R. Okazaki, H. Kawano-Furukawa, T. Shibauchi, H. Harima and Y. Matsuda, *Phys. Rev. B* **76**, 132507 (2007).
 - ¹⁶ A. Llobet, A. D. Christianson, W. Bao, J. S. Gardner, I. P. Swainson, J. W. Lynn, J.-M. Mignot, K. Prokes, P. G. Pagliuso, N. O. Moreno, J. L. Sarrao, J. D. Thompson and A. H. Lacerda, *Phys. Rev. Lett.* **95**, 217002 (2005).
 - ¹⁷ S. Majumdar, G. Balakrishnan, M. R. Lees, D. McK. Paul and G. J. McIntyre, *Phys. Rev. B* **66**, 212502 (2002).
 - ¹⁸ M. Blume, A. J. Freeman and R. E. Watson, *J. Chem. Phys.* **37**, 1245 (1962).
 - ¹⁹ S. Raymond, E. Ressouche, G. Knebel, D. Aoki and J. Flouquet, *J. Phys.: Condens. Matter* **19**, 242204 (2007).
 - ²⁰ W. Bao, G. Aeppli, J. W. Lynn, P. G. Pagliuso, J. L. Sarrao, M. F. Hundley, J. D. Thompson and Z. Fisk, *Phys. Rev. B* **65**, 100505(R) (2002).
 - ²¹ N. Aso, private communications.
 - ²² C. Stock, C. Broholm, J. Hudis, H. J. Kang and C. Petrovic, *Phys. Rev. Lett.* **100**, 087001 (2008).
 - ²³ Swee K. Goh, J. Paglione, M. Sutherland, E. C. T. O'Farrell, C. Bergemann, T. A. Sayles and M. B. Maple, cond-mat/0803.4424 (unpublished).
 - ²⁴ L. D. Pham, T. Park, S. Maquilon, J. D. Thompson and Z. Fisk, *Phys. Rev. Lett.* **97**, 056404 (2006).
 - ²⁵ M. Nicklas, O. Stockert, T. Park, K. Habicht, K. Kiefer, L. D. Pham, J. D. Thompson, Z. Fisk and F. Steglich, *Phys. Rev. B* **76**, 052401 (2007).